

## A preparation and Characterization of Functionally Graded Aluminum Alloy Based Composite Via Casting Route

Mohammed M. Abdullah

Abdulhaqq A. Hamid

Mechanical Engineering Department  
College of Engineering, Mosul University, Mosul - IRAQ

### Abstract

In the current study, stir and centrifugal casting apparatus have been designed and constructed for the preparation of cast functionally graded aluminium alloy (AA4043) based composites containing Silicon Carbide (SiC) reinforcement particles. Hardness of different cast functionally graded composites (FGCs.) processed with different rotating speeds have been investigated. Unreinforced base alloy and cast gravity composite corresponding to the composition of matrix alloy of cast FGCs have also been cast and characterized for the purpose of comparison. The present study aims to understand the influence of rotating speed of mould on the reinforcing particles distribution and hardness of the resulting cast FGCs. It was found that increasing the processing speed of mould increases the level of distribution of reinforcing particles from the inner to the outer region. At a given processing speed, hardness increases significantly with increasing the radial distance for the both top and bottom surfaces and could be attributed to the segregation of the reinforcing particles at the outer region.

**Key Words:** Functionally graded composite: Processing speed: SiC particles.

تحضير ودراسة خصائص المواد المترابطة الدقائقية والمنتجة وظائفيا والتي أساسها سبيكة الألمنيوم منتجة بتقنية السبابة

محمد مثنى عبدالله  
عبد الحق عبد القادر حامد  
قسم الهندسة الميكانيكية- كلية الهندسة- جامعة الموصل- موصل/العراق

### الخلاصة

تم في هذه الدراسة تصميم وتصنيع منظومتى سبابة هما منظومة السبابة بالمزج والتي يتم عن طريقها تحضير المادة المترابطة المنتجة وظائفيا من خلال مزج مادة الأساس (AA4043) مع دقائق التقوية (SiC)، ومنظومة السبابة بالطرد المركزي التي يتم من خلالها إنتاج مواد منتجة مترابطة. تم في هذا البحث دراسة الصلادة لمواد منتجة وظائفيا مكونة من مادة الأساس (AA4043) ومقواة بدقائق (SiC) منتجة بتقنية السبابة بالطرد المركزي وعند سرعة دورانية مختلفة. ولغرض إجراء المقارنة بين هذه المواد تم كذلك تكوين وتصنيع سبيكة (AA4043-SiC) منتجة بتقنية سبابة المزج وسبيكة (AA4043) من دون دقائق التقوية (SiC) وتحت نفس ظروف التصنيع للمواد المنتجة التركيب. إن الهدف من هذا البحث هو دراسة تأثير سرعة دوران القالب على توزيع دقائق التقوية والصلادة للمواد المنتجة وظائفيا. ولقد وجد عند زيادة سرعة تدوير القالب فإنه يؤدي إلى زيادة عدم تجانس وجود دقائق التقوية داخل مادة الأساس من داخل إلى خارج سطح النموذج. وعند سرعة دورانية محددة، لوحظ زيادة قيم الصلادة بزيادة المسافة من داخل إلى خارج سطح النموذج ومن جهتي الأعلى والأسفل. ويمكن إن يعزى ذلك إلى اندفاع دقائق التقوية إلى خارج

من داخل إلى خارج سطح النموذج ومن جهتي الأعلى والأسفل. ويمكن إن يعزى ذلك إلى اندفاع دقائق التقوية إلى خارج

Received: 2 – 5 - 2012

Accepted: 1 – 4 - 2014

## 1- Introduction:

Composite materials are produced when two different materials are mixed to give a combination of properties that cannot be attained in original materials. Composites may be selected to give unusual combinations of stiffness, strength, weight, high temperature performance, corrosion resistance, hardness and conductivity [1,2]. Functionally Graded Materials (FGMs) are motivated by the need for properties that are unavailable in any single material and the need for graded properties to offset adverse effects of discontinuities for layered materials. Thus, in FGMs, the constituents vary in some direction enabling these materials to provide unique performance [3].

The best method to fabricate of the FGMs is the centrifugal method. The technique uses the centrifugal force generated by a rotating cylindrical mould to throw the molten metal against the mould wall and forms the desired shape. In centrifugal casting the mould rotates at a predetermined speed [4]. A controlled non-uniform microstructure with continuously changing properties FGMs reinforced with different ceramic particle could be produced by centrifugal casting technique to obtain these graded properties, which are not achievable in monolithic or homogenous materials [5]. Zhang et.al. [6] have produced the FGMs by *in-situ* centrifugal casting that used ( $Mg_2Si$ ) as a reinforcement particles and Al as a matrix material. The mould is shaped as tube. The results show the outer region of tube having more  $Mg_2Si$  than the inner region of tube. Yoshimi et al [7] have studied the microstructures and composition gradients in Al-SiC, Al-Shirasu (volcanic eruptions commonly found in south Kyushu in Japan), Al- $Al_3Ti$ , Al- $Al_3Ni$  and Al- $Al_2Cu$  FGMs have been investigated. The Al-SiC, Al-Shirasu and Al- $Al_3Ti$  FGMs are fabricated by the centrifugal solid particle method where the distribution particles of SiC, Shirasu and  $Al_3Ti$  are solids in the melts. The results show that the volume fraction of the SiC and  $Al_3Ti$  increases towards to the outer region due to increasing the G-factor. On the other hand, Al- $Al_3Ni$  and Al- $Al_2Cu$  FGMs are fabricated by the centrifugal *in-situ* method where Al- $Al_3Ni$  and Al- $Al_2Cu$  systems have lower liquidus temperatures than the processing temperatures to compare these microstructures with *ex-situ* composites. Zenon [8] has fabricated and characterized the FGMs Al-Mg alloys with *in-situ* particles ( $AlB_2$ ) composites using centrifugal casting. The results show that the *in-situ*  $AlB_2$  particles segregation toward the external zone of the cast piece, resulting in higher hardness and micro-hardness in this region.

The present research work have been directed to the influence of key processing parameters, namely processing mould speed on the microstructure has been determined and their impact on the hardness behaviour of the resulting FGCs has been evaluated. The knowledge base generated through this study is expected to lead to an understanding of the relationship between rotational speed, microstructure and hardness and may contribute to the identification of critical factors of processing in order to control the properties of these FGCs. Moreover, it is, also, expected to offer a better understanding of the potential and limitations of FGMs, which have already emerged as an advanced engineering material.

## 2- Experimental Work:

Commercial Aluminium - Silicon (AA4043) was chosen as the matrix alloy for studies on current cast FGCs. The molten Al-Si alloy was, also, alloyed by the addition of the required amount of Magnesium (Mg) of 2 wt.%. The presence of magnesium is well known to enhance the wettability of SiC particles in molten aluminium alloy due to a limited chemical

reaction at the particle-alloy interface [2]. The chemical compositions of the commercial aluminium-silicon alloy, in total weight percent, as determined by optical spectrometer analyzer (portable-X-MET 3000 TX), used in solidification processing of different cast FGCs, composites and unreinforced alloys are given in Table (1). The chemical analysis was determined by the help of a workshop center at Northerner Cement Company (Mosul-Nineveh).


**Table (1):** Chemical composition of the Aluminium Alloy (AA4043).

Aluminium Association Grade	Cu wt.%	Ni wt.%	Si wt.%	Fe wt.%	Zn wt.%	Al wt.%
AA4043	0.15	0.01	4.5- 6	0.59	0.12	Balance

SiC powder with average particle size of 231  $\mu\text{m}$  was selected on the basis of reasonably low cost and easy availability, Also, the SiC particle, is well known, as a highly wear resistance and of good mechanical properties, including high-temperature strength and thermal shock resistance. The selected SiC particles were manufactured by Avonchem, Mseclesfied, Cheshire, United Kingdom (UK).

A batch type of stir casting set-up, as shown in **Fig. 1** was used in this investigation, for the fabrication processing of all different cast FGCs, composites and unreinforced base alloy. The set-up consisted of a melting unit and a stirring arrangement. The melting unit was an electrical resistance heating vertical furnace. A calibrated chromel-alumel thermocouple was used to control the temperature of the furnace by placing it close to the wall. The temperature controller, having a range of 0-1400  $^{\circ}\text{C}$  with a control accuracy of  $\pm 5$   $^{\circ}\text{C}$ , was used. For melting of aluminium alloy, a cylindrical tapered clay-graphite crucible with flat bottom was used. The crucible had an average diameter of 125 mm and was placed inside the furnace as shown in Fig.1. The stirrer was driven by 1/2 Horse Power (HP) motor having four rated speeds of 700, 900, 1100 and 1300 rpm for stirring the melt. The motor of the stirrer was held rigidly over the furnace by a gripping arrangement centrally fixed with steel frame structure of the set-up as shown in **Fig.1**. The stirrer was fixed to the shaft of motor by gripping coupling arrangement. The rigid base structure of the stirrer arrangement was containing a lifting device for controlling the position of the stirrer in the crucible. A suitable funnel was placed near the stirrer rod for incorporating reinforcing particles into molten aluminium alloy. All composites and unreinforced base alloy were prepared by the above arrangement [9].

**Figures 2 and 3** show the constructed centrifugal casting set-up used in the current study [9]. The centrifugal set-up consisted of a rotating steel mould as shown in **Fig. 4**, electrical motor, heating system and temperature controller. The steel mould was mounted on one end of the vertical shaft of the electrical motor by using coupling arrangement unit. The circular heating elements were kept around the mould, leaving sufficient clearance, in order to heat the mould and delay the solidification process of the composite slurry. The electrical connection to the heating element was driven through an autotransformer to control the power input to the heaters. A calibrated chromel-alumel thermocouple was used to control the temperature of the chamber by placing it close to the mould wall. The following subdivision paragraphs explain and describe in more details all the essential parts included in the above centrifugal set-up.

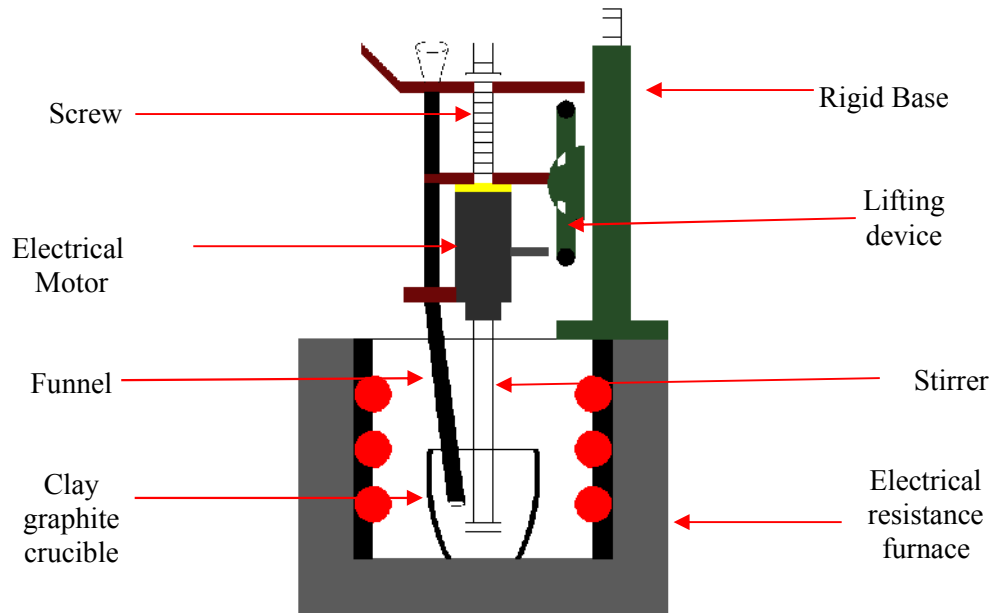

**Figure (1):** Diagram showing the stir casting arrangement used in the current



**Figure (2):** Photograph of centrifugal casting apparatus.

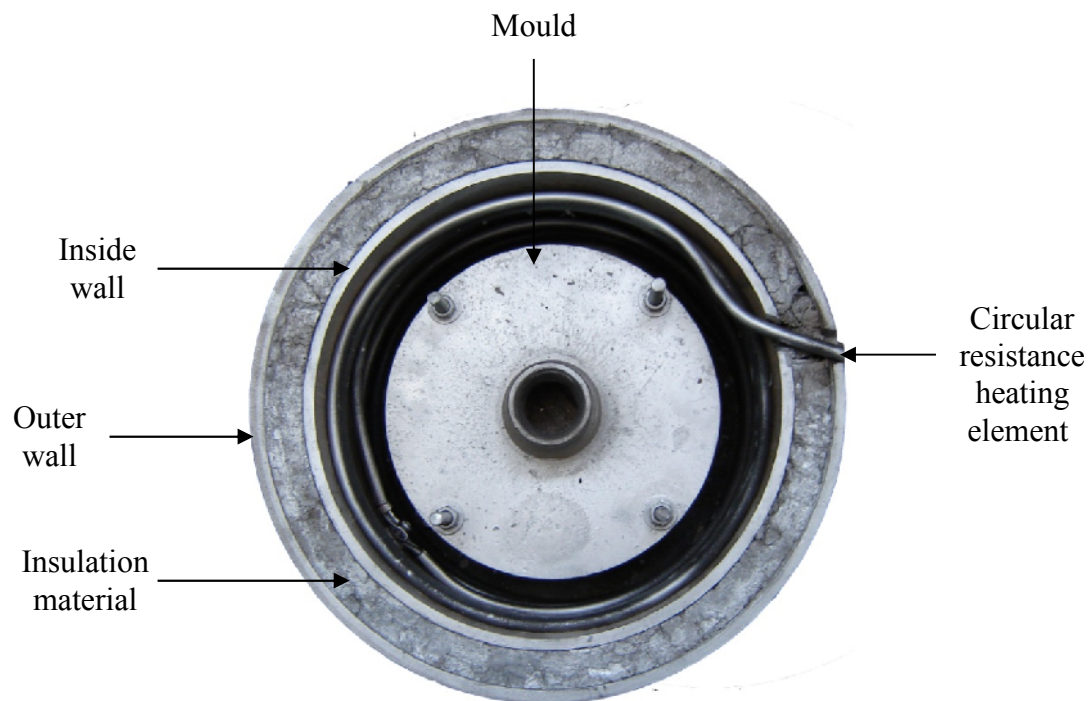


Figure (3): Photograph of heating unit of centrifugal casting set-up.



Figure (4): Photograph of the assembly of mould.


Near about 1kg of commercially aluminium alloy was melted in the clay-graphite crucible inside the main furnace at desired processing temperature of 850 °C. Before any addition, the surface of the melt was cleaned well by skimming. At the same time, the mould of centrifugal casting was prepared and heated up to about 500 °C. Prior to addition, the weighed amounts of SiC particles and magnesium were preheated to about 200 °C by putting them near the gate of the main furnace head. Magnesium was wrapped by aluminium foil to prevent it from oxidation and burning and added to the melt alloy at desired processing temperature. The preheated stirrer was used to mix and dispersed the magnesium in the molten alloy. After that, a desired amount of preheated SiC particles was added slowly at the rate of approximately 4 g/min to the melt. The speed of stirrer was kept constant in all experiments at about 900 rpm. A digital strobometer was used to measure the stirring speed. The position of the stirrer inside the melt was always kept constant at the given level. The temperature of the melt was kept constant for all experiments and measured by using a temperature indicator connected to a chromel-alumel thermocouples placed at depth of 15-20 mm inside the melt during the stirring. The temperature of the melt slurry was maintained within 750 °C of the processing temperature. When the desired time (about 15-20 minute) elapsed, the speed of the stirrer was brought down slowly till stopped. Then, the clay-graphite crucible was removed from the main furnace by using a special designed hand lifting device. The melt slurry was, then, poured into a preheated centrifugal mould; the heaters are switch off. The centrifugal casting mould is rotated about 15 minute to ensure the solidification the cast FGCs. The pouring process was kept as close as possible to the top of the mould leaving only the necessary clearance to ensure minimum exposure of the slurry to the surrounding environment. No degassing practice of the slurry or melt was carried out at any stage of processing. In order to study the influence of the processing speed of mould on the microstructure and consequently on the mechanical properties, different speeds of rotation of the mould were used, namely 1000, 1250, 1500, 1750 and 2000 rpm.

Cast unreinforced alloys having chemical composition of aluminium, magnesium and silicon, similar to that of the matrix alloy of the cast FGCs, were prepared using the same set-up and procedures stated above, but without any addition of SiC particles. These casting alloys were used for the comparison of the microstructures and the mechanical properties with those obtained in the different cast FGCS. Also, cast gravity composites having chemical composition and constituents nearly similar to that of the FGCs were prepared using the same set-up and procedures stated above, with the same amount of the SiC particles addition, but without rotation of the mould. Also, these casting composites were used for the comparison of the microstructures with those obtained in different cast FGCs and unreinforced alloys.


#### 4: Results and Discussion:

Figures 5 and 6 show the dimensions of test specimen after machining out from the cast ingot and the scheme of sectioning the cast ingot of FGCs, gravity composite and unreinforced alloys was used to prepare specimens for metallographic studies respectively. The typical unetched optical microstructure of unreinforced alloy (AA4043) is shown in **Fig.7**. The microstructure consists of precipitates of intermetallic phase (Al-Si) forming due to the presence of silicon in the matrix alloy beyond the limit of solid solubility. Some dark areas of porosity are also visible. The cast unreinforced alloy has been prepared for comparison with the matrix microstructure of different cast FGCs.


The typical unetched optical microstructure of cast particulate ordinary aluminium alloy based composite contained 33 vol.% of reinforcing SiC particles and similarly processed as that of FGCs but without rotation of mould is shown in **Fig.8**. It is generally observed that the matrix alloy was enriched by the reinforcing SiC particles. Also, it is observed that the SiC particles are more or less uniformly distributed in the matrix alloy of cast composite. Some dark areas of porosity are also visible. The cast composite has been prepared for comparison with the different cast FGCs.

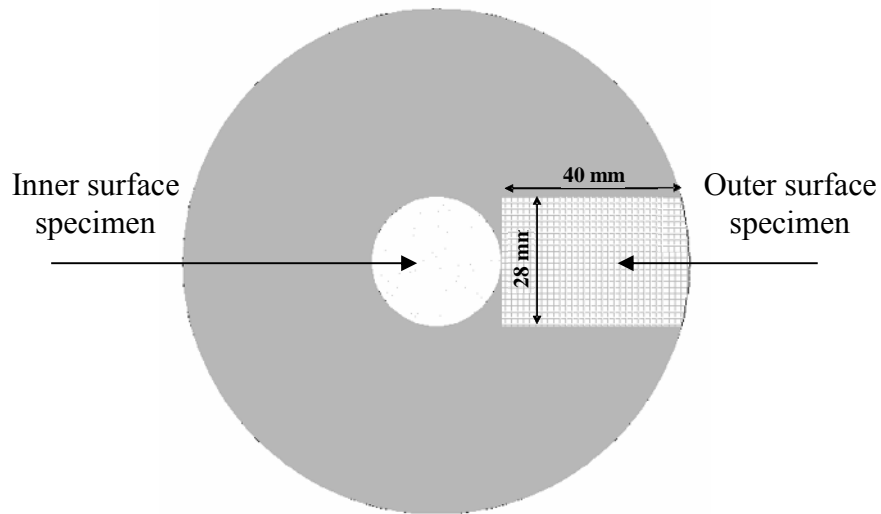


**Figure (5):** The test specimen after machining-out.

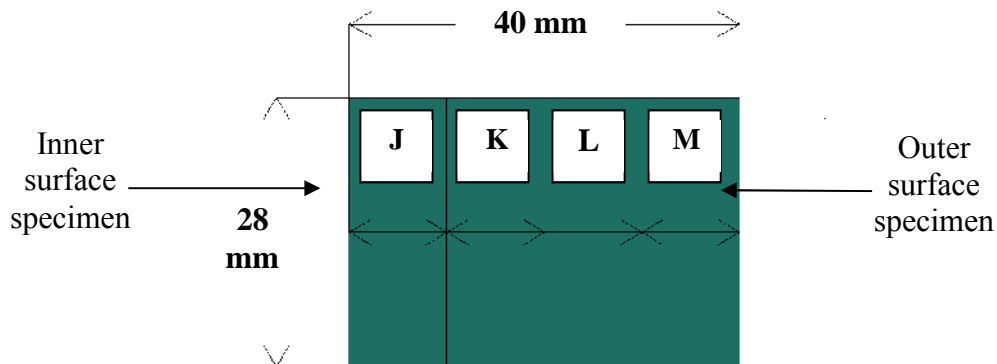

**Figure (6):** The specimen used in microstructure test, each section having an equal dimension of 10 mm.

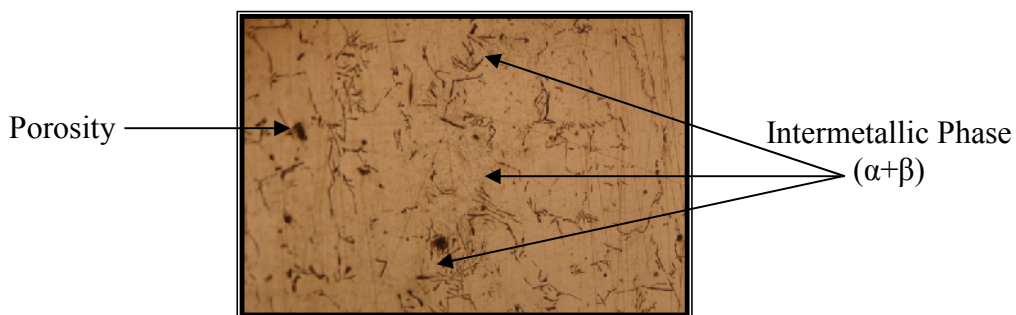


**Figure (7):** Typical unetched optical microstructure of unreinforced alloy, X85.

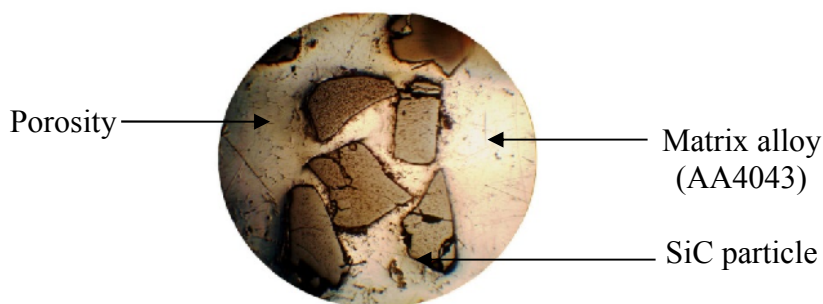

**Figure (8):** Typical unetched optical microstructure of cast particulate composite containing 33 vol% SiC particles without rotation of mould, X50.

**Figure 9** shows a typical unetched optical microstructure of cast particulate aluminium alloy-based FGCs and it mainly consists of SiC particles imbedded in the matrix alloy. The interesting feature is the porosity attached to the reinforcing particles as shown in **Fig.9**. These porosities may use the surfaces of the poorly wetting particles as potent sites for bubble nucleation and the bubble may remain attached to these particles [10].


Cast FGCs containing 33 vol.% of reinforcing SiC particles, have been developed at different processing speeds of mould while the other processing parameters are maintained constants. The unetched optical particles distribution of FGCs cast at different processing speeds of mould are shown in **Figs. 10-14**. The particles distribution reported in the present study relate to those observed in the middle height segment of the cast specimen unless stated otherwise. It was observed that as the processing speed of mould increases, the amount of reinforcing particles in the outer region of the cast ingot increases. It is well known, that the moving direction of the reinforcing particle under the effect of centrifugal force is determined by the magnitude of the densities difference

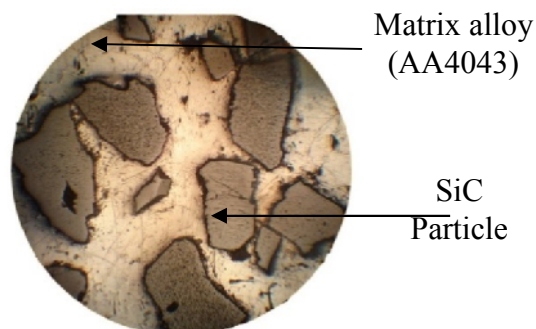


**Figure (9):** Typical unetched optical microstructure of cast FGCs containing 33 vol% SiC particles, X50.




of particle and matrix alloy. Since, the density SiC is larger than that of the matrix alloy, more amount of SiC particles is expected that in the outer region obtained in high processing speed of mould as shown in **Figs. 10-14**.

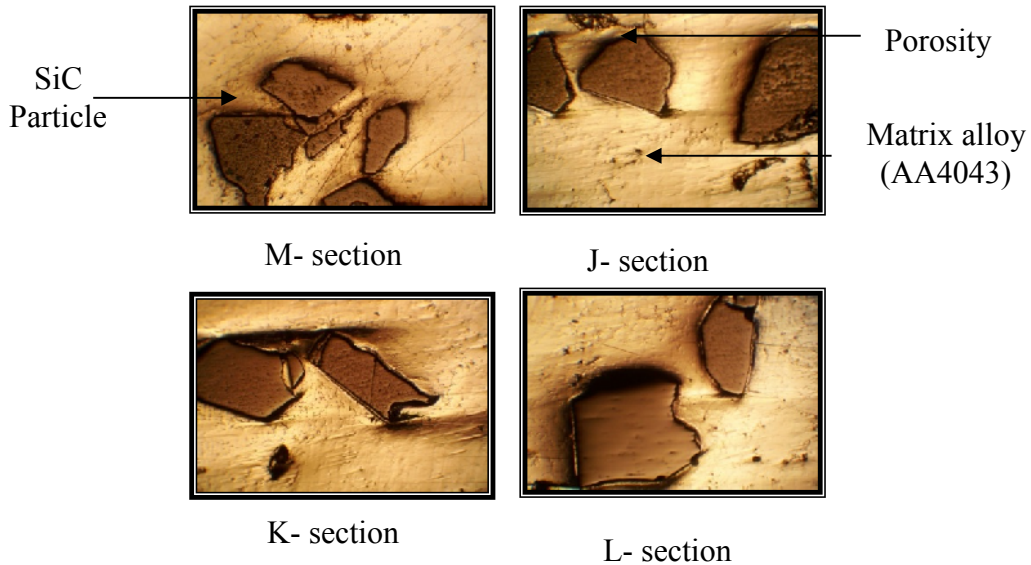


**Figure (10):** Unetched optical microstructure of cast FGCs containing 33 vol.% of SiC particles, synthesized at processing speed of 1000 rpm, X63.

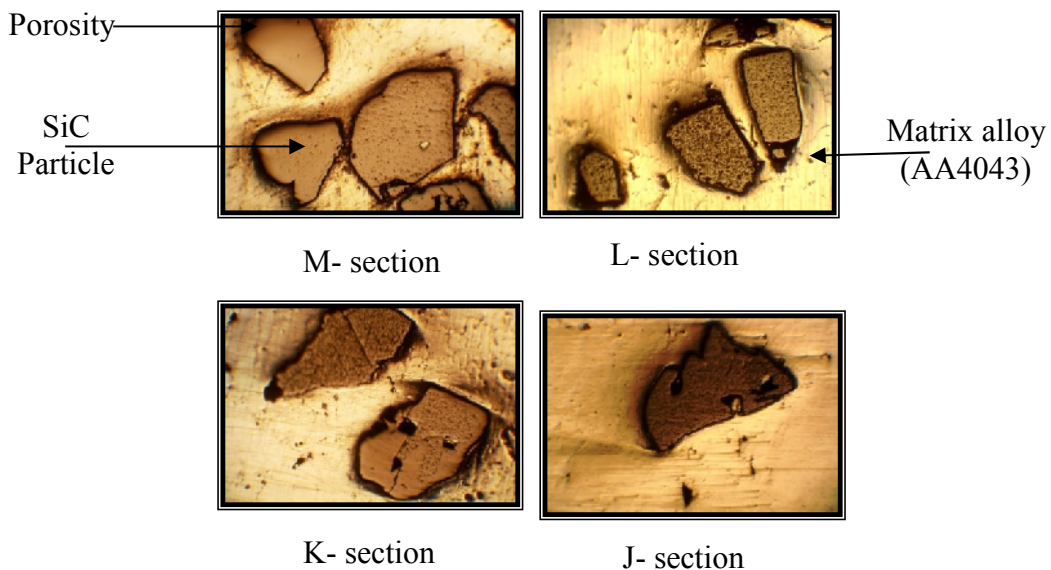


**Figure (11):** Unetched optical microstructure of cast FGCs containing 33 vol.% of SiC particles, synthesized at processing speed of 1250 rpm, X63.

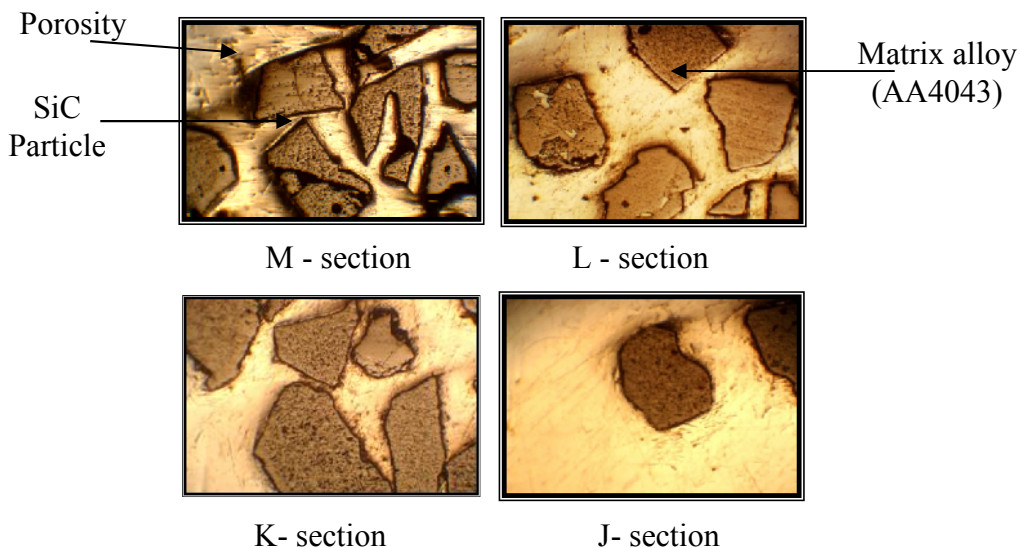

**Figure (12):** Unetched optical microstructure of cast FGCs containing 33 vol.% of SiC particles, synthesized at processing speed of 1500 rpm, X63.

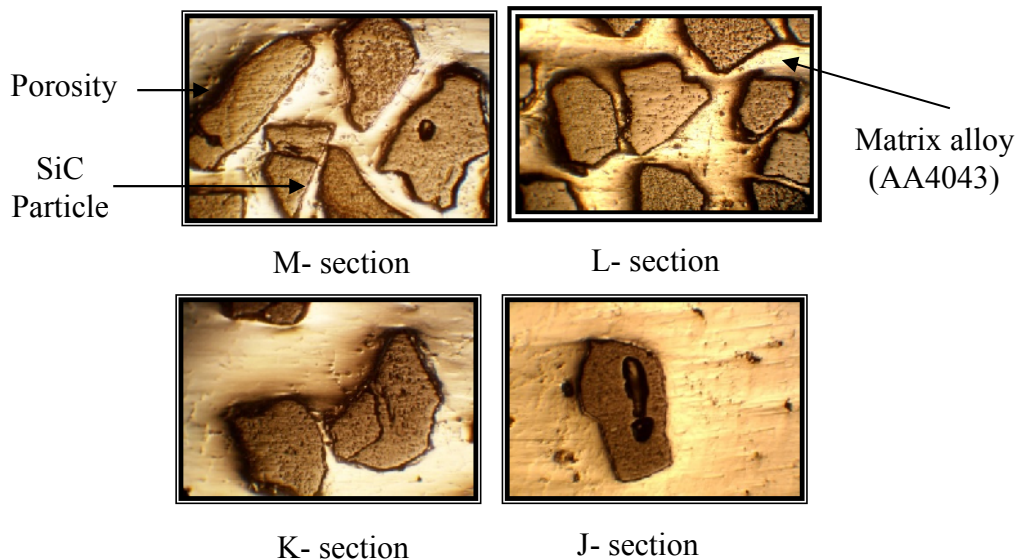


**Figure (13):** Unetched optical microstructure of cast FGCs containing 33 vol.% of SiC particles, synthesized at processing speed of 1750 rpm, X63.

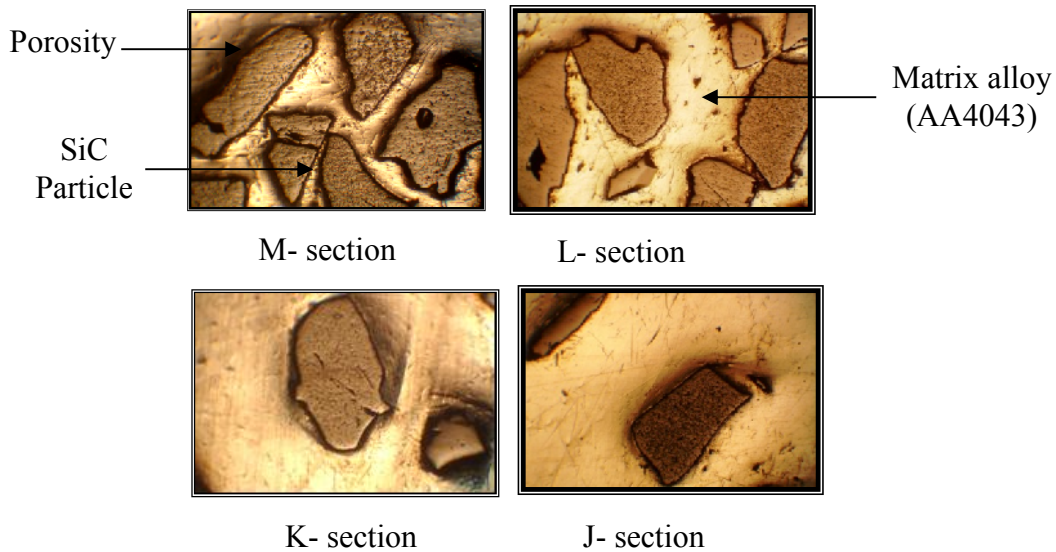

**Figure (14):** Unetched optical microstructure of cast FGCs containing 33 vol.% of SiC particles, synthesized at processing speed of 2000 rpm, X63.


For comparison, cast aluminium alloy based composites have been developed and processed in a way similar to that of FGCs but without rotation of mould. **Figure 15** shows the unetched optical particles distribution of cast Al-SiC composite. It is observed that the SiC reinforcing particle is more or less uniformly distributed from inner to outer region of the cast ingot.

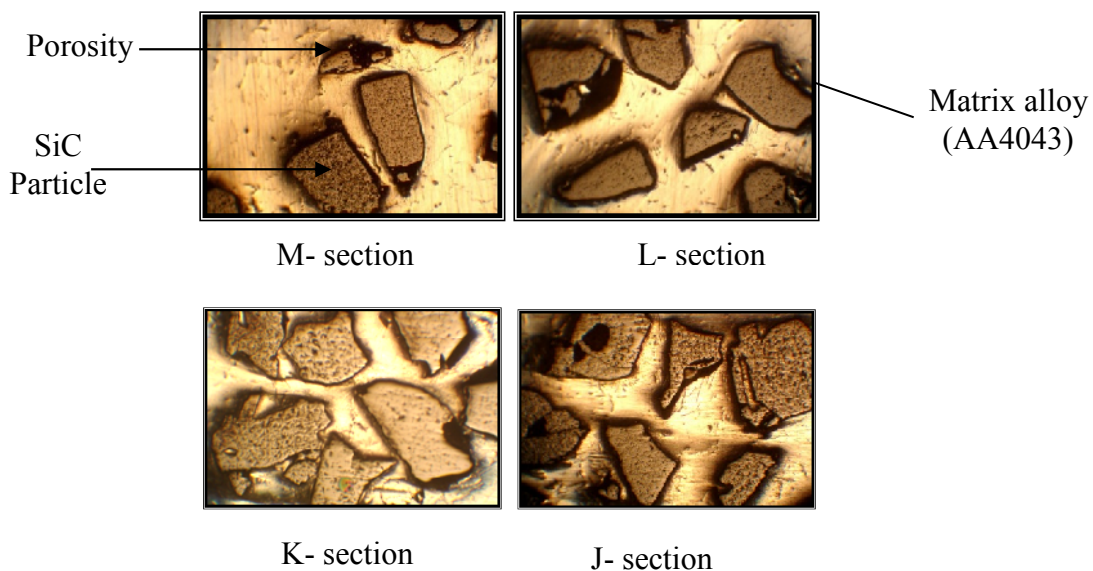

**Figure (15):** Unetched optical microstructure of cast (AA4043- SiC) composite without mould rotation at different regions from outer to inner region, X63.

In the present study, the reinforcing particles phase was observed as grayish areas under optical microscope. Dark black areas were also observed and treated as porosity.

The image analyzer software program was used for estimating Area Fraction ( $A_f$ ) at each section for all FGCs and cast composite. Representative image had been selected at a given section in the cast FGCs specimen and the value of the analysis of these images was reported as the  $A_f$ . **Figure 16** shows the variation of  $A_f$  with increasing distance for different cast FGCs. It is observed from **Fig. 16** that, for a given processing speed, the estimated  $A_f$  increases significantly with increasing radial distance from inner to outer region for all different cast FGCs. Also, it is observed that the  $A_f$  increases significantly at outer region with increasing processing speed of mould from 1000 to 2000 rpm. At the same time, the  $A_f$  decreases slightly at the inner region with increasing processing speed. Thus, the increased  $A_f$  at the outer region and reduced  $A_f$  at the inner region, could be attributed to the movement of reinforcing particles. As the processing speed of mould increases, the effect of centrifugal force increases and the relatively denser SiC particles move outward and segregate at the outer region.

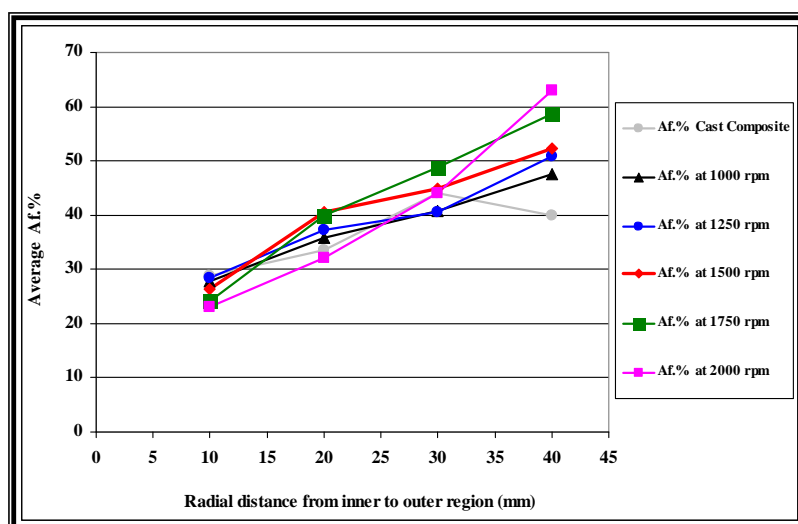

**Figure (16):** Area fractions ( $A_f$ ) for the all FGCs specimens at different processing speed of rotation mould and cast composite.

In order to identify the role of processing speed of mould on the  $A_f$ , The  $A_f$  of the present cast FGCs has been compared with that observed in cast composite processed similarly as the cast FGCs but without any rotational speed of mould. The result of  $A_f$  for cast composite is shown in the same figure. It is observed that the  $A_f$  is more or less constant with increasing radial distance from inner to outer region. This indicates that there is more homogeneity in the distribution of reinforcing particles in the cast composite compared with that in FGCs.

The variation in Rockwell hardness with radial distance from the inner to the outer region for cast unreinforced alloy, cast composite and cast FGCs processed at 1000 1250, 1500, 1750 and 2000 rpm, is shown in **Fig. 17** (a and b); (a) for top surface and (b) for bottom surface. It is observed from the figure that hardness remains nearly constant with

increasing radial distance from inner to the outer region for cast unreinforced alloy. Also, it is observed that there is little difference in hardness between top and bottom surfaces.

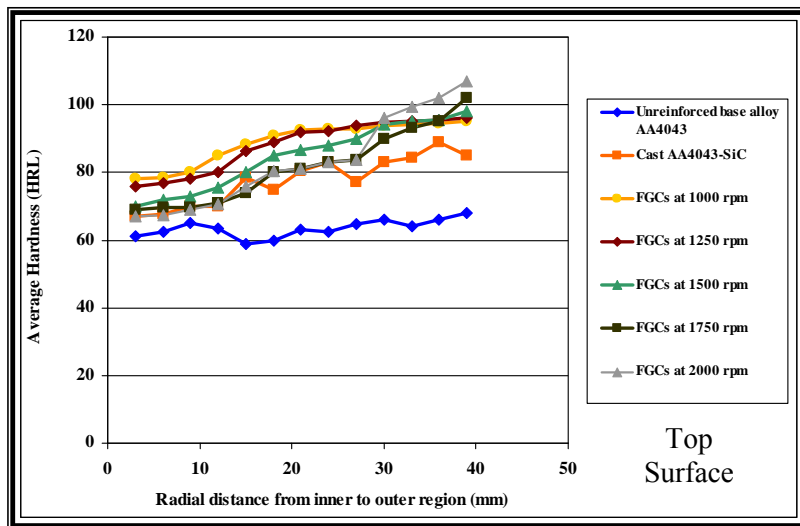


Figure (17a): The variation of average Rockwell (C) hardness with radial distance for cast unreinforced alloy, cast composite and all cast FGCs.

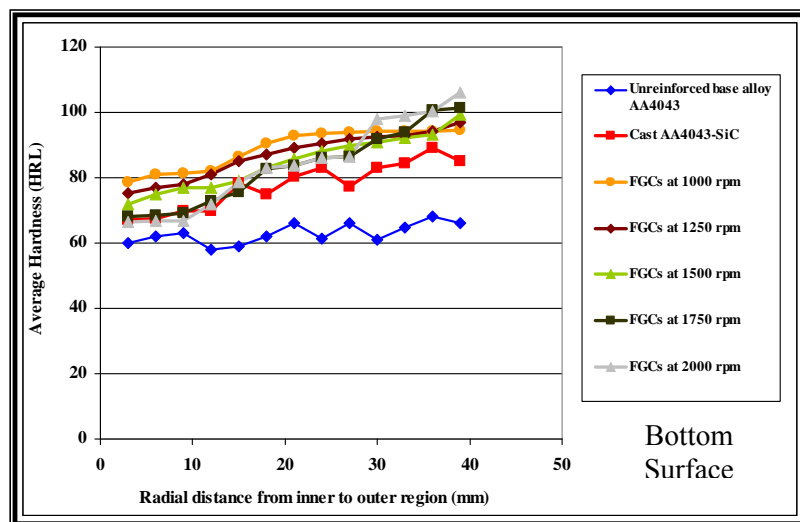


Figure (17b): The variation of average Rockwell (C) hardness with radial distance for cast unreinforced alloy, cast composite and all cast FGCs.

The variation in hardness with radial distance for cast composites similarly processed as that for unreinforced alloy and FGCs is also shown in the same figure. The hardness increases slightly with increasing radial distance. There is no significant difference in the average hardness between the top and bottom surfaces with increasing radial distance, as observed from Fig. 17.

If one compares the hardness of cast unreinforced base alloy with that of cast composite containing 33 vol.% reinforcing particles, it appears that the hardness of the cast composite increases significantly than that of cast unreinforced alloy and this could be attributed to the addition of the reinforcing particles in the matrix alloy.

For all cast FGCs, the hardness increases significantly with increasing radial distance for the top and the bottom surfaces of the cast specimen. At a given processing speed (say, for example, 2000 rpm), the hardness reached a maximum value at the outer region of cast FGCs and could be attributed to the segregation of the reinforcing particles at the outer region, the gradient in the value of hardness from inner to outer region is acute. The segregation of reinforcing particles occurs mainly due to the effect of centrifugal force generated and applied to the semisolid mixture of slurry composite melt which lead to the formation of the desired composition gradient.

The observation of porosity content from the survey of images of different FGCs and composite shows that there is no significant difference in the porosity content, in both materials. But, in case of cast FGCs, the porosity, which is mainly originated from the gases dissolved in the melt during processing increases significantly with increasing distance from inner to outer region (as particle content increasing) of the resulting cast specimen. Also, it is observed that there is little increase in porosity content with increasing processing speed of mould, particularly at higher speed. Thus, the increased porosity content in the resulting cast FGCs, developed at higher processing speed of mould could be attributed to the increase in particle content at the outer region of the resulting cast specimen.

The hardness of cast FGCs are expected to be better than those of cast unreinforced alloy due to the reinforcement of matrix alloy by SiC particles. Also, it is expected that the mechanical properties to be better than those of cast composites for the same volume fraction of the reinforcing particles. The reason for this improvement is mainly due to less porosity content in FGCs as compared to that for cast composites.

## 5- Conclusions:

The main conclusions may be drawn from the current study are:

- 1- There is a considerable increase in the hardness of cast composite over those of the cast unreinforced base alloy. This has been attributed to the reinforcement of matrix alloy by SiC particles.
- 2- Increasing processing speed of mould increases the extent of inhomogeneity of the particle content along the radial distance of the cast FGCs.
- 3- Increasing processing speed of mould increases the hardness at the outer region of FGCs and reached maximum value at processing speed of 2000 rpm.
- 4- Increasing processing speed of mould decreases the hardness at the inner region of FGCs and reached minimum value at processing speed 2000 rpm.
- 5- Little differences in hardness from inner to the outer region of cast composite are possibly due to the inhomogeneous distribution of reinforcing particles and, also, possibly due to the dominating influence of porosity.
- 6- There are little differences in particle content between the top and bottom surfaces of all different cast FGCs processed at different processing speeds.

## **6- References:**

- [1]- Donald, R. A., "The Science and Engineering of Materials" Third S.I Edition, United Kingdom (UK), p.549, (1998).
- [2]- ASM Handbook committee "Composites" Vol. 21, p.130, (2001).
- [3]- Gomes J.R., Ribeiro A.R, Vieira A.C, Miranda A.S and Rocha L.A, "Wear Mechanisms in Functionally Graded Aluminium Matrix Composites: Effect of the Lubrication by an Aqueous Solution" FCT- Portugal, pp.1-6, (2002).
- [4]- James, P. S., Ashok, S, Stephan. D. A, Thomas.H. S and Steven. B. W "The Science and Design of Engineering Materials", 2<sup>th</sup> Edition, United States, p.578, (1999).
- [5]- Manoj Kumar B.V, Bikramjit .B, Murthy V.S.R and Manoj Gupta "The role of tribochemistry on fretting wear of Mg–SiC particulate composites" Composites: Part (A) 36, pp. 13-23, (2005).
- [6]- Zhang J, Wang Y. Q, Zhou B.L and Xing Q.W "Functionally graded Al/Mg<sub>2</sub>Si *in-situ* composites, prepared by centrifugal casting" Journal of Materials Science, Vol.17, pp.1677-1679, (1998).
- [7]- Yoshimi W, Ick S.K and Yasuyoshi F. "Microstructures of Functionally Graded Materials Fabricated by Centrifugal Solid-Particle and In-Situ Methods" Metals and materials International, Vol. 11, pp.391-399, (2005).
- [8]- Zenon H.M.P "Fabrication and Characterization of functionally graded Al/AlB<sub>2</sub> matrix composites for high aerospace application using centrifugal casting" MSc.Thesis, Mechanical Engineering, University of Puerto Rico, pp.77-85, (2006).
- [9]- Mohammed M.A.A "Study the Characterizations of Aluminium Alloy Based Functionally Graded Composites Produced by casting technique" MSc.Thesis, Mechanical Engineering, University of Mosul, pp.57-79, (2011).
- [10]- Ray, S., "Cast metal matrix composites- Challenges in processing and design", Bulletin of Mater. Sci, Vol.18, No. 6, pp.693-707, (1995).

**The work was carried out at the college of Engineering. University of Mosul**