

Manufacturing of Bricks from Soil and Crushed Limestone by Compression

M. O. Amin

Lecturer

maherz55@yahoo.com

M. A. M. Khidir

Lecturer

Technical Institute of Mosul

A. M. Taher

Assist. Lecturer

Abstract

The environmental impact due to cement and burnt clay industries are increasing continuously, also cement concrete blocks and burnt clay bricks are increasingly becoming costly due to excessive cost of fuel required to manufacture the cement or burning the clay, while the soil suitable for construction is available everywhere in the world. The paper presents the results of an experimental investigation undertaken at Mosul Technical Institute to assess the potential for unfired compressed earth bricks using locally soil as construction material stabilized with crushed limestone obtained from the waste of masonry factories. The wet soil molded into bricks by manual press known globally as CINVA-RAM, exert high pressure. The press was manufactured locally for the research purposes conducted in the institute. Different percentages of crushed limestone by weight (passing sieve No.8) were added namely (4, 8, 12, 16, and 20 %) to the soil obtained from 20 km west of Mosul to reduce its expansiveness if any, and in a trial to improve its characteristics [1]. The results showed increase in compressive strength at 4% and sharp decrease with higher percentages.

Keywords: Unfired compressed earth bricks, CINVA-RAM press, crushed limestone

صناعة طابوق من التربة ومسحوق حجر الحلان باستخدام الضغط

أكرم محمد طاهر

مدرس مساعد

محمد أمين محمد خضر

مدرس

المعهد التقني - موصل

المخلص

ماهر عمر أمين

مدرس

إن التأثيرات البيئية السلبية الناتجة عن استخدام الوقود في صناعة السمنت وفخر الطابوق في تزايد مستمر كذلك فإن مادة الخرسانة على المدى الطويل غير صديقة للبيئة. إن هذه الأسباب بالإضافة إلى العامل الاقتصادي تستدعي التفكير في صناعة مواد بناء بديلة. ومن الطرق المبتكرة والمتميزت استخدامها في العالم خلال العقود القليلة الماضية هي استخدام مكبس للتربة يسلط ضغط عالي قادر على إعطاء حبيبات التربة ترابط ذاتي وقوة تحمل تجعلها صالحة للاستخدام كمادة بناءية في كثير من أنواع التربة بدون الحاجة إلى استخدام مادة رابطة. ومن أجل التعريف بهذه المادة البنائية الجديدة وإجراء البحوث العلمية عليها فقد تم تصنيع المكبس محلياً بنجاح لإنتاج هذه الكتل على مستوى البحوث في المعهد التقني في الموصل. في هذا البحث استخدم مزيج من التربة ومسحوق حجر الحلان الناتج بشكل عرضي. لغرض البحث اضيفت كميات متباينة من مسحوق الحجر المار من منخل رقم (8) إلى التربة وفق النسب (20, 16, 12, 8, 4, 0). أظهرت النتائج زيادة في مقاومة الانضغاط عند النسبة 4% وانخفاض سريع في مقاومة الانضغاط بزيادة مسحوق حجر الحلان، مما يستدعي الحذر من استخدامه بدون دراسة في الطابوق المضغوط وغير المفخور. الكلمات المفتاحية: كتل التربة المضغوطة وغير المحروقة، مكبس سنقارام، مسحوق حجر الحلان

Received: 27 - 5 - 2013

Accepted: 19 - 8 - 2013

1- Introduction

Compressed Earth Bricks, defined as "masonry elements principally made of raw earth, which are small in size and which have regular and verified characteristic obtained by the static or dynamic compression of earth in a humid state followed by immediate demoulding"[2]. Compressed earth blocks owe their cohesion in a humid state and in a dry state essentially to the clay fraction within the earth; an additive can, however, be added to the earth to improve or enhance particular characteristics of the product [3-9]. Growing concern and interest about environmental and ecological issue increased the used of earth as a building material. In comparison with another building material, compressed earth block offered numbers of advantages. It increases the utilization of local material and reduces the transportation cost as the production is in situ, makes quality housing available to more people. Good strength, insulation and thermal properties, less carbon emission and embodied energy in the production phase, create extremely low level of waste, cause no direct environmental pollution during the whole life cycle[16]. Earth brick also have the ability to absorb atmospheric moisture which resulted create healthy environment inside a building for its occupant. According to [11], unfired clay bricks have "14% of the embodied energy of fired bricks and 25% of the embodied energy of concrete blocks."

One of the drawbacks using earth alone as a material for construction is its durability which is strongly related to its compressive strength [8][20][21]. Obtaining a durable material would need a treatment which would result in a sufficient mechanical strength as well as low sensitivity to water. The most common methods employed for the stabilization of clayey soils are cement and lime stabilization [3-9].

In another study [12], an attempt to improve strength and water absorption of blocks stabilized not only by cement but also by lime, bitumen and gypsum, and observes that gypsum and bitumen blocks fail the erosion test; cement & lime addition increase strength and reduce water absorption.

In the present work, we have tried to examine the properties of earth bricks for certain type of soil near Mosul by the addition of crushed limestone.

2- Materials

2-1 Limestone

Limestone is the most widely rock in Iraq and particularly in Mosul area, where it can be extensively used in constructional activities. Limestone consists essentially of calcium carbonate, with which there is generally some magnesium carbonate and siliceous matter such as quartz grains. In order to determine the influence of crushed limestone content as a stabilizer for the mechanical properties of unfired clay bricks, several blends have been used with (0, 4, 8, 12, 16 and 20%).

2-2 Soil

The soil used in the investigation were taken from location 20 km to the west of Mosul city which is chiefly of silt and clay soil, the soil have the following properties L.L. (37) %, P.I. (16) %. Thus the soil is classified as (CL) according to the Unified Classification System and described as "Inorganic clay of low plasticity". The percentage of clay size particles ($\leq 2m$) is 28%.The specific gravity (Gs) is 2.72. The linear shrinkage (8.0) %. The soil was mixed with different amounts of crushed limestone passing sieve No.8, namely (0, 4, 8, 12, 16 and 20%) and a compacting stress sufficient to produce 1.88 gm/cm³ wet density.

3- Testing Of Materials

3-1 Atterberg Limits

The consistency limits of the treated soil were determined after being mixed with (4, 8, 12, 16 and 20%) of the crushed limestone. The results are presented in Table (1). It can be noticed that the liquid and plasticity indices decreased with the increase of the added crushed stones.

Table (1) Atterberg limits of treated and untreated soil

Crushed Limestone passing sieve No.40	0	4	8	12	16	20
Liquid Limits (L.L) %	37	33	29	25	23	20
Plastic Limits (P.L) %	21	20	18	16	15	13
Plasticity Index (P.I) %	16	13	11	9	8	7

3-2 Linear shrinkage

Shrinking of earth blocks when drying out is disadvantages, if they are to be used as building materials. According to [14], shrinkage depends on the type and quantity of clay; Table (2) show that the linear shrinkage reduced from 8.0 to 6.6 % by the addition of the crushed Lime stones CLS. This addition leads to improvement of soil workability, but not to an increase in strength [15].

Table 2. Linear shrinkage of treated and untreated soil

Type of soil	Shrinkage (mm)	Total Length	Percentage
Soil	48	600	8.0
Soil + 4% CLS	46	600	7.6
Soil + 8% CLS	43	600	7.1
Soil + 12% CLS	41	600	6.8
Soil + 16% CLS	40	600	6.6



Figure.1 Shrinkage Testing moulds

3-3 Grain Size Analysis:

Table (3) describes the analysis result. It can be shown that the clay size particles decreased with the increase of crushed Limestone addition, while the percent of silt size particles increased.

Table (3) Comparison of the grain-size analysis results

% Crushed Limestone passing Sieve No. 8	% Clay	% Silt	% Sand
0	28	51	21
4	25	53	22
8	22	55	23
12	19.5	57.5	23
16	16.5	60.5	23
20	14	63	23

(Walker, 1996) states that clay contents of between 5% and 20% are considered suitable for earth block production. The results indicate that the clay proportion (20%) is within the recommended limits required for production of compressed soil bricks. The clay presence is important in the sense that, clay is responsible for the bonding effect amongst the soil particles. The soil also contains sufficient amounts of coarse fraction, i.e. 20% sand by proportion, this amount is sufficient to limit shrinkage of blocks when drying out [14].

3-4 Modified Compaction Test:

The modified proctor test was conducted on soil samples treated with (0, 4, 8, 12, 16 and 20%) of crushed limestone. The samples were compacted at different moisture contents, to obtain the moisture-density relationship. The results are summarized in Table (4). To clarify the difference due to the treatment. It can be noticed that the dry density (γ_d) increases with the amount of crushed stone added up to 4%, and then it tends to decrease. So, it can be said that (4%) addition is the optimum that gives the maximum density.

Table (4) The Modified Compaction Test Results.

% Crushed Limestone passing sieve No. 8	0	4	8	12	16	20
Max. Dry Density (γ_d) kN/m ²		1.69	1.68	1.65	1.66	1.65
Optimum Moisture Content (O.M.C)	20	20	19	18.2	18	18.5

4- Cinva-Ram Press

The compressed earth block is the modern descendent of the moulded earth block. the turning point in the use of presses and in the way in which compressed earth blocks were used for building and architectural purposes came only with effect from 1952, following the invention of the famous little CINVA-RAM press, designed by engineer Raul Ramirez at the CINVA centre in Bogota, Columbia. This was to be used throughout the world. With the 70s and 80s there appeared a new generation of manual, mechanical and motor-driven presses, leading to the emergence today of a genuine market for the production and application of the compressed earth block[18].The press was manufactured locally for the research purposes conducted in the Technical Institute of



Figure.2 CINVA-RAM press

Mosul as shown in Fig.2, producing bricks with dimensions of (290×140×100 mm) as shown in Figs.3&4.



Figure.3 Ready brick for curing



Figure.4 Laboratory-produced unfired brick compared with fired brick

5- Bricks Preparation

The "qualified" soil is dried by spreading it in an open space, larger granules of soil, such as lumps and gravel are removed by sieving with 4 mm sieve; the required quantity of soil was weighted. The ratios of crushed limestone used in the various mixtures investigated were respectively 0, 4, 8, 12, 16 and 20% by weight of semi dry soil. Four ratios of mixing water were used for each of the above soil-crushed limestone mixes 12, 16, 20 and 24%. The mixing was done by small concrete mixer and continued sufficient time to get a homogeneous mixture of constituents. The mixture was then transferred to a CINVA-RAM press for molding. The ejected blocks, see Fig.3, were then placed in a yard and wrapped tightly with plastic cover to preserve the moisture for three days and then damp cured for the maturity about two weeks. After one month the blocks were tested for the unit weight, compressive strength, flexural strength, shrinkage and absorption. Four specimens for each mix were tested for compressive strength and two specimens for flexural strength.

6- Test of Bricks and Discussion of Results

A series of tests are carried out to determine the unit weight, the compressive strength, flexural strength and water absorption of brick samples.

6.1 Compressive Strength Test

Since there is no standard testing for unfired compressed bricks, the compressive strength test for the brick was held according to the ASTM: C67 and that was representing by applying the bricks in their dry curing condition to the test. The compressive strength of the specimen was calculated from the following equation:

$$C = W/A$$

The compressive strength C in MPa was calculated by dividing the breaking load W (maximum load) in Newton's by the average of



Figure.5 Appearance of failure after compressive test

the gross areas *A* of the upper and lower bearing surfaces of the specimen in square millimeters.

6.1.1 Effect of Mixing Water content on Compressive Strength

The water content more convenient for molding the bricks is function of the soil type. To obtain compressed bricks of quality with a certain earth, it is necessary to establish the ideal percentage of water and amount of material to be put in the mold of the press, through an optimization process. The water content is not usually the same obtained by the Proctor test where the maximum density is reached by a dynamic compaction. In the press, the compaction is almost static, what gives a certain difference. Figure 6, shows that the compressive strength of samples tested increases with increasing of mixing water content and the optimum at about 20%. It shows clearly that the compressive strength increases with increasing of mixing water until 20%, which is the optimal mixing water content and then decreases rapidly.

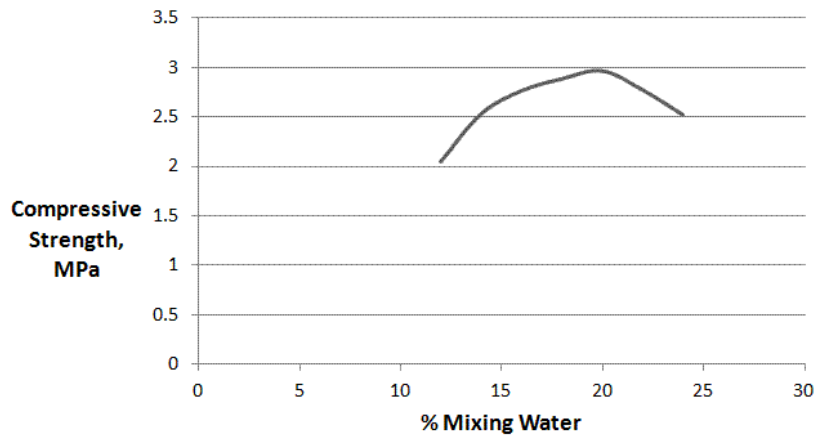


Figure (6): Effect of Mixing water on Compressive Strength

6.1.2 Effect of Crushed limestone on compressive strength

Figure.7 shows that the compressive strength of samples tested increases due to addition of about 3-4% crushed limestone and then rapidly decreases. Increasing of crushed limestone from 4% to 15% has resulted in more than 50% decrease in strength. This graph shows that all the bricks lose strength as the crushed limestone content increases.

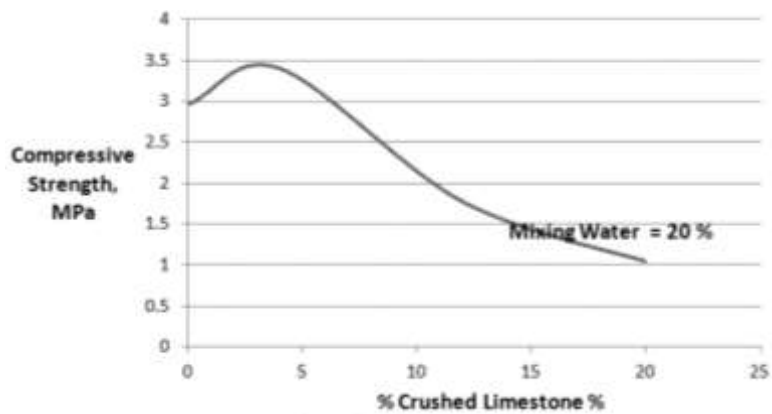


Figure (7): Effect of LS on Compressive Strength

6.2 Flexural Strength Test

Universal testing machine was used to carry out the flexural strength test. The modulus of rupture of each specimen was calculated by using the following formula:

$$f_r = 3PL/2bd^2 \dots\dots\dots(1)$$

Where:

f_r = modulus of rupture of the specimen at the plane of failure, MPa,

P = mid-span concentrated load indicated by the testing machine,

L = distance between the supports, mm,

b = net width of the specimen at the plane of failure, mm,

d = depth of the specimen at the plane of failure, mm.

This formula is used only for measuring the strength of the block, but a minimum acceptable load can also be set. For example, the tested block should withstand a load of 15 blocks to be acceptable [18].

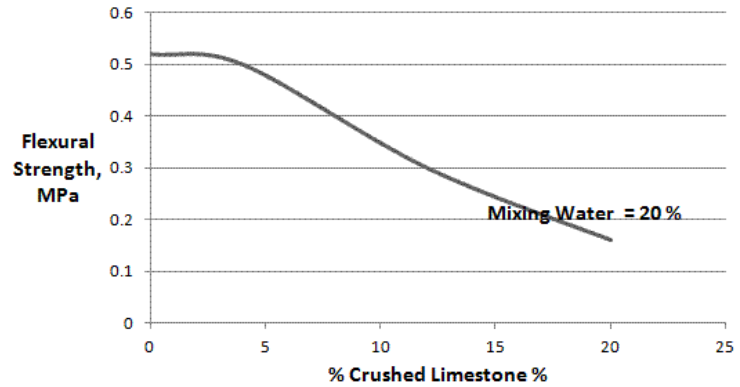


Figure (8): Effect of LS on Flexural Strength

6.3 Clay Brick Densities

Commonly, most researchers found that the density of compressed earth bricks is within the range of 1500 to 2000 kg/m³ [16]. Density of the compressed earth brick is consistently related to its compressive strength and compactive force applied during production. The dry density is largely a function of the constituent material's characteristics, moisture content during pressing and the degree of compactive load applied. The higher density obtained due to compaction significantly increases the compressive strength of the blocks, as well as their resistance to erosion and to damage from water. The unit weights of brick samples are obtained by dividing the mass of the bricks by their overall volume. The average wet density of the units produced as part of this research was 1880 kg/m³. Whereas the general specification (given for a standard block) gives the following limits:

Dry: minimum: 1700 kg/m³; recommended: 2000 kg/m³.

Freshly molded: minimum: 1870 kg/m³; recommended: 2200 kg/m³.

Clearly, the bricks produced just satisfy the minimum standard requirement for freshly molded and does not satisfy the minimum dry density.

6.4 Water Absorption

The absorption capacity of earth blocks gives a general idea on the presence and importance of voids. As the density of soil increased, its porosity is reduced and less water can penetrate it [19]. Water absorption is a function of clay and compacting stress and usually related with the strength and durability of earth bricks and therefore it is important to determine the rate of water absorption of earth bricks. High rate of water absorption of a specimen may cause swelling of clay fraction and resulting in losing strength with time. The test consists of immersing the soil samples in water and measuring the increase in weight after 24 hours. The absorption is evaluated in dry weight percentage. Water absorption test for the samples was failed due to excessive deterioration as shown in Figure.9.

7- Conclusions

In this paper, the influence of adding crushed limestone on the mechanical and physical properties of the unfired compressed soil bricks was presented. The following main conclusions can be drawn from this study:

1. The index properties of the soil were changed by the addition of the crushed stone towards silty characteristics.
2. Compressive strength of unfired compressed soil bricks were improved by the presence of small percentages of crushed limestone not exceeding 4%.
3. Adding more crushed limestone causing rapid decrease of strength, for example at about 15% the strength decreases to about half.
4. The lower compressive strength at high percentages of crushed limestone can be attributed to insufficient cohesion between clay particles and the surrounding soil.
5. It is necessary to make thorough studies before adding crushed limestone to the soil for making unfired compressed bricks.
6. The reduction of the index properties towards less plastic nature indicates that there will be reduction in the swelling potentials.



Figure (9): Appearance of brick after saturation test

8- References

- [1]- Siham I. Al-Azzo, "Treatment of Expansive Clayey Soil in AL-Wahda District at Mosul City with Crushed Limestone". Iraqi Journal of Earth Sciences, Vol. 9, No. 2, pp. 1-10, 2009
- [2]- Compressed Earth Blocks: Standards., 1998. Brussel, Belgium: CDI and CRATerre-EAG Publication.
- [3]- E.A.Adam (2001) "Compress Stabilized Earth Block Manufacture in Sudan."
- [4]- Gooding, D.E.M (1993) "Improved processes for the production of soil cement building blocks", University of Warwick.
- [5]- Peter. W and Trevor. S "Properties of some cement stabilised compressed earth blocks and mortars/Materials and Structures", Vol.30, November 1997, pp 545-551
- [6]- Smith, R.G., "Building with soil-cement bricks", Building Research and Practice (March/April 1974) pp. 98-102.
- [7]- Heathcote, K., "Compressive strength of cement stabilized pressed earth blocks", Building Research and Information 19 (2) (1991) pp. 101-105.
- [8]- Walker, P.J., "Strength, durability and shrinkage characteristics of cement stabilized soil blocks", Cement & Concrete Composites 17 (1995) pp. 301-310.
- [9]- Bell, F.G. 1996. "Lime Stabilization of Clay Mineral and Soil". Eng. Geol. 42, Dept. of Geol. and App Geol. University of Natal, South Africa, pp. 223-237.

- [10]- Oliver, M. and El Gharbi, Z., "*Sisal fibre reinforced soil block masonry*", Proceedings of the Fourth International Masonry Conference, London, October, 1995 (British Masonry Society, Stock-on-Trent, 1995) pp. 55-58.
- [11]- Heath, Andrew. "*Unfired clay bricks.*" Copyright Greenspec 2010. Web. January 22, 2012.
- [12]- Ozkan, E., Al-Herbish, M. S., "An Experimental Study of the Critical Properties of Pressed and Stabilized Earth Bricks". *Architectural Science Review*, Vol. 38, pp. 59-73, 1995
- [13]- Al-Layla, M.T. and Al-Ashou, M.O. 1985. "*Swelling Properties of Mosul Clay*". Proc. Iraqi Conf. on Eng., Baghdad-Iraq, pp. 18-23.
- [14]- Minke, G., "*Earth Construction Handbook*". WIT Press, Boston, 2000.
- [15]- Bell, F.G., 1996. "*Lime stabilization of clay minerals and soils*". *Engineering Geology*, 42(4): 223-237.
- [16]- Fetra, V. R., and et al "*Preliminary Study of Compressed Stabilized Earth Brick (CSEB)*" *Australian Journal of Basic and Applied Sciences*, 5(9): 6-12, 2011.
- [17]- Walker, P., "*Specifications for Stabilized Pressed Earth Blocks*". *Masonry International*, 10, (1), pp. 1-6, 1996.
- [18]- Vincent Rigassi, "*COMPRESSED EARTH BLOCKS: Manual of production*" by CRATerre-EAG.
- [19]- Houben, H., Guillaud, H., (CRATerre), "*Earth Construction*" (1984). Primer Brussels, CRATerre / PGC / CRA / UNCHS / AGCD.
- [20]- Venkatarama Reddy BV, "*Sustainable materials for low carbon buildings*".
- [21]- Venkatarama Reddy BV, Jagadish KS. Influence of soil composition on the strength and durability of soil-cement blocks. *Indian Concret J* 1995;69:517–24.

The work was carried out at the Technical Institute of Mosul